

HANDBOOK OF VINYL FORMULATING

SECOND EDITION

EDITED BY
RICHARD F. GROSSMAN




HANDBOOK OF VINYL FORMULATING

SECOND EDITION

Edited by

Richard F. Grossman

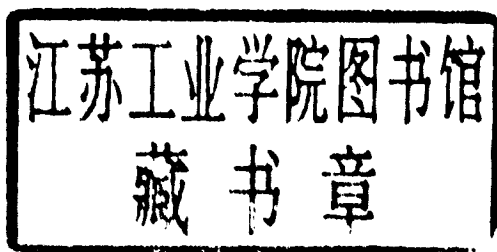

 **WILEY-
INTERSCIENCE**

A JOHN WILEY & SONS, INC., PUBLICATION

Copyright © 2008 by John Wiley & Sons, Inc. All rights reserved.

Published by John Wiley & Sons, Inc., Hoboken, New Jersey
Published simultaneously in Canada

No part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, mechanical, photocopying, recording, scanning, or otherwise, except as permitted under Sections 107 or 108 of the 1976 United States Copyright Act, without either the prior written permission of the Publisher, or authorization through payment of the appropriate per-copy fee to the Copyright Clearance Center, Inc., 222 Rosewood Drive, Danvers, MA 01923, 978-750-8400, fax 978-750-4470, or on the web at www.copyright.com. Requests to the Publisher for permission should be addressed to the Permissions Department, John Wiley & Sons, Inc., 111 River Street, Hoboken, NJ 07030, 201-748-6011, fax 201-748-6008, or online at <http://www.wiley.com/go/permission>.

Limit of Liability/Disclaimer of Warranty: While the publisher and author have used their best efforts in preparing this book, they make no representations or warranties with respect to the accuracy or completeness of the contents of this book and specifically disclaim any implied warranties of merchantability or fitness for a particular purpose. No warranty may be created or extended by sales representatives or written sales materials. The advice and strategies contained herein may not be suitable for your situation. You should consult with a professional where appropriate. Neither the publisher nor author shall be liable for any loss of profit or any other commercial damages, including but not limited to special, incidental, consequential, or other damages.

For general information on our other products and services or for technical support, please contact our Customer Care Department within the United States at 877-762-2974, outside the United States at 317-572-3993 or fax 317-572-4002.

Wiley also publishes its books in variety of electronic formats. Some content that appears in print may not be available in electronic format. For more information about Wiley products, visit our web site at www.wiley.com.

Library of Congress Cataloging-in-Publication Data:

Handbook of vinyl formulating

Handbook of vinyl formulating / Richard Grossman. — 2nd ed.
p. cm.

Rev. ed. of : Handbook of polyvinyl chloride formulating / Edited by Edward J.

Wickson. 1st ed. 1993.

Includes index.

ISBN 978-0-471-71046-2 (cloth)

1. Polyvinyl chloride. I. Title.

TP1180.V48H36 2008

668.4' 236 — dc22

2007033461

Printed in the United States of America

10 9 8 7 6 5 4 3 2 1

HANDBOOK OF VINYL FORMULATING

**WILEY SERIES ON PLASTICS ENGINEERING AND
TECHNOLOGY**

Series Editor: Richard F. Grossman

Handbook of Vinyl Formulating, Second Edition / Edited by
Richard F. Grossman

PREFACE TO THE SECOND EDITION

As Ed Wickson stated in the Preface to the First Edition, the *Handbook of Vinyl Formulating* is the only text devoted to that topic. It has been highly successful; copies are in the hands of most of the vinyl technologists in North America and many throughout the world. Vinyl formulating has developed considerably in a number of areas since 1993. The Second Edition addresses these developments.

Certain of the chapters of the First Edition have been combined. “Antidegradants,” for example, covers antioxidants, heat stabilizers, light stabilizers and biocides. The reason is that, in formulating, the technologist must consider all of these in developing a stabilization package. Presentation in a single chapter enables correlation without repetition. Similarly, “Fillers and Reinforcements” combines several chapters. The technologist is encouraged not to look at individual ingredients but to look at all in a given class, to experiment with several and, when needed, to innovate useful blends. To this end, suggestions are included regarding experiments that have not as yet been reported but that seem interesting.

There has been a conscious effort to avoid material better suited to more specialized texts in order to concentrate on formulation. This does not include rationalization as to why ingredients have the effects observed, since such theorizing is vital to innovation. Another factor important in product development is intellectual satisfaction. To that end, authors and editor have done their best not to be boring.

RICHARD F. GROSSMAN

Wilmington, DE

PREFACE TO THE FIRST EDITION

Although superseded by polyethylene as the world's number one plastic, polyvinyl chloride (PVC) retains its title as the most versatile of all plastics—both in the number of ways it can be processed and in the range of end products. This is due to (a) the wide variety of PVC resin types available (varying in molecular weight and distribution, homo-, co-, and terpolymers, particle size and distribution, morphology, crystallinity, etc.) and (b) the ability of PVC to be formulated with a multitude of additives, unmatched by any other plastic.

There is a wealth of information on PVC technology available in various scientific and trade journals, proceedings of technical meetings, and technical literature of suppliers of PVC resins and additives. There are also several excellent books on the broad aspects of PVC technology and on additives for plastics. However, none focuses on PVC formulating. This volume is the end result of what the editor had long felt was a need for a one-volume, ready-reference book describing in detail the properties of the various commercial PVC resins available in the United States and Canada and how these, together with additives, are used in formulating PVC. Related chapters cover economics of formulating, basic statistics and design of experiments, laboratory compounding and test methods, and environmental and health concerns in formulating vinyl compounds. Although emphasis is on formulating in this book, separate chapters are also included on dry blending, powder coatings, plastisol and organosol preparation, and electron beam radiation curing because these are not all covered in currently available books.

Because of its complexity, there is probably no one person who could claim to be truly expert on all aspects of the resins and additives used in PVC formulating. With this in mind, the editor chose experts well qualified in their particular field to author the various chapters. The reader is encouraged to contact these experts for additional information.

Acknowledgments (in alphabetical order) with profound thanks are due the following individuals who contributed helpful advice in reviewing parts of the manuscript: William J. Casey, Consultant; Robert D. Dworkin, Akzo Chemicals; Ved P. Gupta, Synergistics Industries; Leonard G. Krauskopf, Exxon Chemical Company; Subhash Lele, Engelhard Corporation; Gary R. Mitchener, Halstab Division, Hammond Lead; Warren F. Moore, AT&T; Joseph O'Brien, C. P. Hall Company; Arthur W. Opsahl, DuPont Company; James T. Renshaw, Monsanto Chemical Company; Thomas A. Resing, Littleford Bros.; Robert Reichard, Occidental

Chemical Corporation; Robert C. Ringwood, Consultant; Donald A. Seil, BFGoodrich Company; and A. Nelson Wright, Synergistics Industries.

Special thanks are due my wife, Ann, for help and encouragement, including surrendering the living room during the preparation of the manuscript.

EDWARD J. WICKSON

Baton Rouge, LA
March 1993

CONTRIBUTORS

William D. Arendt, Velsicol Chemical Corp., Northbrook, IL

Mark T. Berard, Dow Chemical Co., Plaquemine, LA

Robert S. Brookman, Teknor Apex Corp., Providence, RI

James H. Bly, retired, Radiation Dynamics

Richard J. Burns, Nova Chemicals Inc., Leominster, MA

R. J. Del Vecchio, Technical Consulting Services, Cary, NC

Jeremy H. Exelby, Schering Polymers, Cheshire, England

Thomas H. Ferrigno, Improbe, Trenton, NJ

Allen D. Godwin, ExxonMobil, Baytown, TX

J. R. Goots, retired, North Olmsted, OH

Richard F. Grossman, RFG Consultants, Wilmington, DE

David M. Henshaw, retired, New Castle, DE

L. Horvath, Aries Industries, Cleveland, OH

Makarand Joshi, Velsicol Chemical Corp., Northbrook, IL

Paul Kroushl, Nexans Cable, New Holland, PA

Leonard G. Krauskopf, Consultant, Plainsboro, NJ

John T. Lutz, Jr., deceased

William R. Mathew, Americhem, Inc., Cuyahoga Falls, OH

M. Fred Marx, retired, Suwanee, GA

Laurent M. Matuana, Michigan State University, MI

B. Mikofalvy, retired

Michael P. Moore, retired

John C. Morley, Plastics Color & Compounding, Dayville, CT

Paul Y. Moy, Supresta US, Ardsley, NY

R. R. Puri, Schering Polymers, Cheshire, England

Sara Robinson, R. T. Vanderbilt Co., Charlottesville, VA

Ashok Shah, retired

Michael K. Stockdale, retired

Kenneth B. Szoc, retired

George W. Thacker, PVC Technical Services, Silver City, NM

C. Michael Vanek, Dow Chemical, Plaquemine, LA

Pierre Verrier, Consultant, St. Cloud, France

Lewis B. Weisfeld, Consultant, Philadelphia, PA

Marvin Whitley, deceased

Edward J. Wickson, Wickson Product Research, Baton Rouge, LA

CONTENTS

Preface to the Second Edition	vii
Preface to the First Edition	viii
Contributors	xi
1. Formulation Development	1
<i>Edward J. Wickson and Richard F. Grossman</i>	
2. Resin Selection for PVC Applications	13
<i>Paul Kroushl</i>	
3. PVC Special Products	57
<i>J. R. Goots, Michael P. Moore, Kenneth B. Szoc, Richard J. Burns, and James H. Bly</i>	
4. Antidegradants	77
<i>George W. Thacker, Richard F. Grossman, and John T. Lutz, Jr.</i>	
5. Colorants for Vinyl	135
<i>William R. Mathew and Richard F. Grossman</i>	
6. Fillers and Reinforcements for PVC	151
<i>Sara Robinson, Thomas H. Ferrigno, and Richard F. Grossman</i>	
7. Monomeric Plasticizers	173
<i>Allen D. Godwin and Leonard G. Krauskopf</i>	
8. Specialty Plasticizers	239
<i>William D. Arendt and Makarand Joshi</i>	
9. Formulating Vinyl for Flame Resistance	287
<i>Paul Y. Moy</i>	
10. Impact Modification	305
<i>Mark T. Berard and C. Michael Vanek</i>	
11. Processing Aids for PVC	315
<i>C. Michael Vanek and Mark T. Berard</i>	
12. Lubricants and Related Additives	327
<i>Richard F. Grossman</i>	

13. Plastisol Technology	371
<i>Ashok Shah, B. Mikofalvy, L. Horvath, and Richard F. Grossman</i>	
14. Formulating Expanded Products	379
<i>Jeremy H. Exelby, R. R. Puri, David M. Henshaw, and Richard F. Grossman</i>	
15. Alloys and Blends	393
<i>Michael K. Stockdale, Robert S. Brookman, and Richard F. Grossman</i>	
16. Flame Retardants and Smoke Suppressants	403
<i>John C. Morley and Richard F. Grossman</i>	
17. Vinyl Wood Fiber Composites	415
<i>Laurent M. Matuana and Richard F. Grossman</i>	
18. Laboratory Methods	433
<i>M. Fred Marx, Marvin Whitley, Pierre Verrier, and Richard F. Grossman</i>	
19. Regulatory and Legislative Matters Affecting the Plastics Industry: Health, Safety, and the Environment	467
<i>Lewis B. Weisfeld</i>	
20. Formulating Flexible PVC for Molding and Coating	491
<i>Richard F. Grossman</i>	
21. Formulating Rigid PVC for Extrusion	503
<i>George A. Thacker</i>	
22. Design of Experiments	515
<i>R. J. Del Vecchio</i>	
Index	529

Formulation Development

EDWARD J. WICKSON and RICHARD F. GROSSMAN

1.1	Introduction	1
1.2	Effects of Formulation on Processing	2
1.3	Effects of Formulation on Properties	3
1.4	Compound Development Procedure	7
1.5	Cost of Ingredients	8
1.6	Specific Gravity of Ingredients	9
1.7	Design of Experiments	11
	References	12

1.1 INTRODUCTION

Polyvinyl chloride (PVC, vinyl) became a major factor in commercial manufacture of flexible goods after World War II, replacing rubber, leather, and cellulose in many areas. As processing technology developed, unplasticized (rigid) PVC began expansion into replacement of metal, glass, and wood, a trend that continues and which now consumes the greatest part of PVC usage. The acceptance of PVC is based on its performance-to-cost ratio. A broad range of useful properties, such as stability, weatherability, inertness to many media, and inherent flame and microbial resistance, are available, with proper formulating, at low cost.

PVC is the thermoplastic polymer most easily varied in properties through formulation. Filler levels vary from a few parts per 100 of resin (phr) in pressure pipe to hundreds of phr in extruded cove base or calendered floor tile. The latter could reasonably be described, based on the most prevalent ingredient, as marble rather than vinyl flooring. In other applications, plasticizer levels as high as 70 phr are common. PVC compounds invariably contain heat stabilizers and lubricants (or ingredients that do both). They may contain fillers, plasticizers, pigments, antioxidants, biocides, flame retardants, antistatic agents, impact modifiers, processing aids, and other

ingredients, including other polymers. Formulation is therefore complex. The goal of this text is to make the process easier to understand and carry out.

1.2 EFFECTS OF FORMULATION ON PROCESSING

The aim of the formulator should be to develop a robust compound, that is, one that will process satisfactorily and yield acceptable properties even if processing or service conditions deviate from those anticipated or thought ideal. This must be done within certain cost parameters. Therefore, the goal, in practice, is to develop the best compound that the application can afford. This should be considered rational formulating. The alternative—development of the lowest-cost compound that can possibly be processed or manage to conform to expectations in testing or service—usually creates more problems than it solves. Although this text is directed primarily to the formulator of rational compounds, it is anticipated that others, radically constrained by cost considerations, may find guidance as well.

The formulation that is optimum today may not be so next year. If it is optimum in one plant, even on one processing line, it may be less so on another. The adaptability of PVC to various processing techniques is stimulation to the ingenuity of the plastics engineer. PVC compounds are calendered, extruded, molded by various techniques, coated, and cast. In these applications, processing begins with a blending step in which additives are mixed with PVC resin. The result may be a (more or less) dry blend, plastisol, organosol, blended latex, or solution. The blending step is followed by fluxing and fusion in the product-forming step (usually the case with rigid PVC) or in a separate pellet-forming step prior to product manufacture. The latter is common with plasticized (flexible) PVC, particularly if the pelletized compound is to be transported to another location, for example, the factory of a customer.

The rate of dry blending can be of concern if it is output-limiting. Although this may be affected by a number of ingredients, it is primarily dependent on the PVC resin and particular plasticizer. Certain resins are designed for rapid plasticizer uptake. Plasticizer type (polarity), viscosity, and solvent power are key factors. These, however, are usually determined by the application rather than ease of incorporation. Typically, processing is adjusted to suit the formulation, by such steps as preheating the plasticizer and following a judicious order of addition of ingredients. Dry blending and blending of solution vinyl, latexes, plastisols, and organosols are discussed in specific chapters of this book.

The resin is of key importance, whether fluxing rigid or flexible compositions. Examples of fast-fluxing resins include low-molecular-weight (low *K*-value) homopolymers and vinyl acetate copolymers. Plasticizers that are strongly solvating, such as butyl benzyl phthalate (BBP), increase flux rate. Again, the selection of both resin and plasticizer is usually dictated by the application. Therefore, the choice of other ingredients, particularly lubricants, stabilizers, and processing aids, is used to increase or decrease the rate of fusion.

In large-volume rigid PVC applications, dry blend is used directly to manufacture articles such as pipe, siding, and window profiles. Certain high-volume flexible

applications, such as extrusion of wire coverings, are also often run from dry blend. Most flexible compounds are, however, fluxed and pelletized, using the combination of an internal batch mixer and a pelletizing extruder, an extruder that can do both, or a combination of extruders. In melt processing, viscosity and friction with metal surfaces are not only obvious factors needed for fusion and pellet formation, but also limitations of output, causes of equipment wear, and potential sources of PVC degradation. This, of course, is also the case with processing to form specific articles. All of the above are influenced critically by formulation and by selection of processing equipment. The extremes of the interaction of formulation and processing in the thought processes of formulators are as follows:

1. The optimum compound having the best available properties-to-cost ratio is developed. Then processing equipment yielding the greatest output and consistency is put into place and duplicated as new facilities are built. This scenario is the case with most high-volume rigid PVC applications and underlies the rapid growth of this sector in North America. A consequence is that suppliers of equipment and of ingredients are driven to cooperate by development of new and improved products.
2. At the other extreme, formulation is continued, often endlessly, to generate compounds that manage to conform to product expectations after on-the-edge processing, using a variety of equipment that happens to be on hand, or that may be obtained at the lowest investment. This is the case with certain flexible PVC applications. It is an important cause of market share decline from offshore competition and displacement of PVC by newer systems, for example, by thermoplastic elastomers.

1.3 EFFECTS OF FORMULATION ON PROPERTIES

In unplasticized compounds, structural rigidity (flexural strength) increases with increasing molecular weight (MW). Up to a point, filler addition increases flexural strength, while impact modifiers and processing aids tend to cause a decrease unless they also function as heat distortion improvers.

Tensile strength, on the other hand, tends to level off as MW is increased, although low extension modulus parallels flexural strength. Abrasion and creep resistance, as with plastics generally, increase with increasing MW, as does cut through resistance. Filler addition can improve both properties to the extent to which particle size and shape create structure in the composition.

Chemical and oil resistance also improve with increasing MW, as does resistance to heat distortion. The attributes that decline with increasing MW are, of course, output and ease of processing. Thus, formulation includes the use of additives that improve the flow of compositions based on high-MW resin, and those that tend to compensate for the choice of a lower-MW alternative. It has, in fact, been suggested that a key purpose of additives is to correct problems introduced by other additives.¹

Compounds containing about 25 phr active plasticizer, such as di-2-ethylhexyl phthalate (DOP:100 percent tensile modulus about 3300 psi) are considered semirigid. Low extension tensile modulus is a reasonable measure of the flexibility of plasticized PVC. It increases somewhat with increasing MW and decreases strongly with increasing plasticizer content. Above about 35 phr DOP, or plasticizer with comparable activity, PVC is considered flexible. At 50 phr, 100% tensile modulus has dropped to about 1700 psi, and at 85 phr, about 650 psi, indicating a highly flexible compound. Lower levels of a more efficient plasticizer will generate comparable data, while less efficient ones would have to be used at higher levels. In plasticized compounds, tensile strength increases more or less linearly with increasing resin MW. Plasticizer type and level have a more profound effect. Both tensile strength and elongation often, but not always, decrease with increasing filler level. Tear strength improves with increasing MW, as does abrasion resistance, but these also depend on the effects of additives. Copolymerization with vinyl acetate leads to similar effects as plasticizer addition, often with fewer associated side effects, but usually at higher cost.

The major factors affecting low-temperature brittleness and flexibility are the level and type of plasticizer. Compounds for low-temperature service most often use blends of standard with special-purpose low-temperature plasticizers (e.g., di-2-ethylhexyl adipate (DOA)). Plasticization typically decreases chemical, solvent, and oil resistance. This can be countered by use of polymeric plasticizers, with attendant increase in cost and typical loss of processing ease, or by means of blends and alloys with highly oil-resistant polymers such as acrylonitrile–butadiene rubber (NBR).

One of the major uses of flexible PVC is in wire coverings. The service rating determines the choice of plasticizer, chosen so as to resist volatilization during the heat aging tests needed to qualify. Loss of plasticizer is the major cause of decreased elongation after heat aging. For service in dry locations, most such compounds use calcium carbonate (CaCO_3) filler. The level is adjusted to balance material cost versus requirements such as abrasion and cut through resistance. Insulations for service in wet locations, where testing (in North America) requires stable volume resistivity for 6 months in 75 °C or 90 °C water, are best served instead with electrical grades of calcined clay. For such service, the plasticizer and other ingredients must be electrical grades. Long-term wet electrical requirements necessitate close quality control of all materials.

Plasticized PVC compounds can have flame resistance ranging from slow-burning, when flammable plasticizers are used, to self-extinguishing when compounded with the halogen synergist antimony oxide, flame-retardant plasticizers, and hydrous fillers such as aluminum trihydrate (ATH) or magnesium hydroxide. Although hydrous fillers add to heat stability, flame-retardant (FR) plasticizers usually require higher levels of stabilizer. Hydrous fillers also reduce smoke generation by promoting oxidation of hot carbon particles (water gas reaction). This reaction is thought to go through metal carbonyl intermediates and is catalyzed by compounds of metals that form carbonyls. The most commonly used is molybdenum, in the form of ammonium octamolybdate (AOM), which reacts at useful temperatures. Flame resistance is increased and smoke generation decreased by fillers that promote formation of a thermally conductive glassy char during combustion. These include hydrous fillers

and certain zinc compounds, notably zinc borate and hydroxystannate. The use of zinc compounds typically requires higher stabilizer levels. This is not the case with antimony oxide, but its use increases smoke generation. Thus, the compounding of highly FR flexible PVC requires complex balancing of ingredients. The overall balance of physical and FR properties of suitably compounded FR flexible PVC is very much better than that of “halogen-free” polyolefin substitutes. The latter typically are so overextended with hydrous fillers that the polymer is no more than a binder.

Rigid PVC foamed composites, consisting of solid layers above and below a foam core, have become increasingly accepted in pipe, siding, and plastic lumber. In addition to weight and cost reduction, thermal conductivity of vinyl siding is decreased, and lumber products are more readily nailed or sawn. Flexible PVC foamed products are most often run from plastisols, as in continuous vinyl flooring, and may be made mechanically by introducing air with strong agitation, or chemically with blowing agents, most often azodicarbonamide. The latter is readily activated by a number of additives, often components of the heat stabilizer, known in such cases by the jargon “kicker.” Surfactants are used to improve cell structure quality, which is also dependent on resin and plasticizer choice.

Light stability and weatherability are provided in a number of ways. The outer layer (topcoat) of vinyl siding or window profile will contain sufficient titanium dioxide (TiO_2) of a suitable grade. Its high dielectric constant enables absorption of a quantum of light and dissipation of energy as heat before a lower-energy photon is emitted. This limits the extent to which incident light is capable of initiating chain reaction free-radical oxidation. Carbon black, again of suitable grades, has the same effect and is widely used in cable jackets and agricultural sheeting. It is, of course, useful to have products that are other than white, black, or gray. Pigments that behave similarly to TiO_2 are used in vinyl siding provided in colors. Other strategies include use of light-resistant topcoats such as acrylics and polyvinyl difluoride (PVDF) over a PVC substrate. Acrylic coatings are also used over PVC plastisol impregnated polyester mesh in flexible signage backgrounds to provide improved printability and resistance to plasticizer migration as well as light stability. In such cases and in other clear and brightly colored products, organic ultraviolet (UV) light absorbers are included. These function in an analogous manner to carbon black and TiO_2 . A photon of light is absorbed, driving the UV light absorber into an excited state. The latter is resonance-stabilized and persists long enough to dissipate energy as (more or less) harmless heat. Additives that are strictly light absorbers, such as hydroxybenzophenones and benzotriazoles, are not antioxidants—in fact, they require antioxidant protection. A newer class of materials, hindered amine light stabilizers (HALS), are not only antioxidants but participants in a chain-reaction antioxidant action. The use of HALS in PVC is now in exploratory stages.

Weatherability of PVC compounds is studied in a variety of devices that simulate sunlight. There is only relative correlation between these methods and actual outdoor exposure. The effects of outdoor exposure itself vary from location to location. There is even suspicion that accelerating outdoor aging using magnification of sunlight introduces variability. Nevertheless, these methods are useful in comparing one compound with another, and the results are often thought predictive of field service by