


FOCUS

MATERIALS SCIENCE SERIES

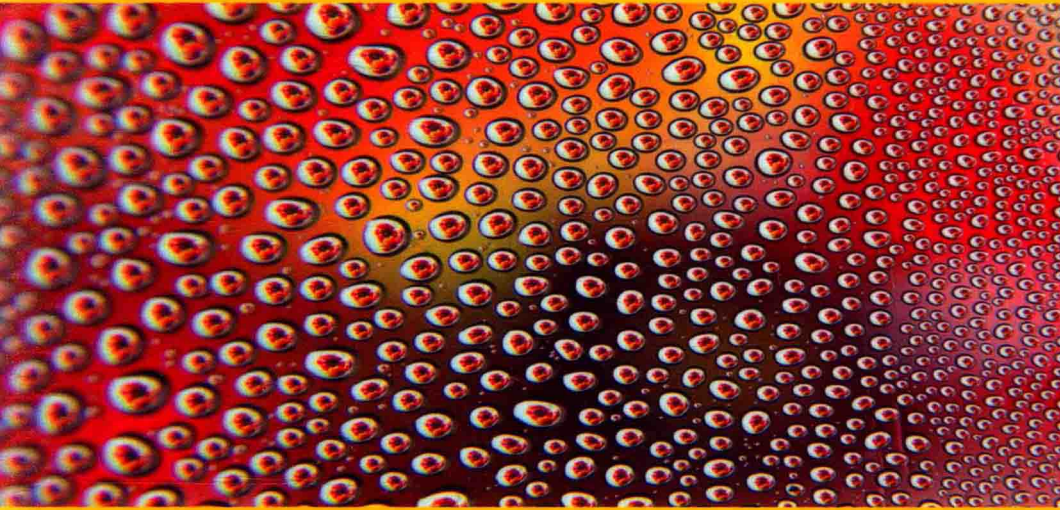

Physical Chemistry and Acid-Base Properties of Surfaces

Jean-Charles Joud
Marie-Geneviève Barthés-Labrousse

ISTE

WILEY

FOCUS SERIES

Series Editor **M**ichel Pons

Physical Chemistry and Acid-Base Properties of Surfaces

Jean-Charles Joud
Marie-Geneviève Barthés-Labrousse

ISTE

WILEY

First published 2015 in Great Britain and the United States by ISTE Ltd and John Wiley & Sons, Inc.

Apart from any fair dealing for the purposes of research or private study, or criticism or review, as permitted under the Copyright, Designs and Patents Act 1988, this publication may only be reproduced, stored or transmitted, in any form or by any means, with the prior permission in writing of the publishers, or in the case of reprographic reproduction in accordance with the terms and licenses issued by the CLA. Enquiries concerning reproduction outside these terms should be sent to the publishers at the undermentioned address:

ISTE Ltd
27-37 St George's Road
London SW19 4EU
UK

www.iste.co.uk

John Wiley & Sons, Inc.
111 River Street
Hoboken, NJ 07030
USA

www.wiley.com

© ISTE Ltd 2015

The rights of Jean-Charles Joud and Marie-Geneviève Barthés-Labrousse to be identified as the authors of this work have been asserted by them in accordance with the Copyright, Designs and Patents Act 1988.

Library of Congress Control Number: 2015952414

British Library Cataloguing-in-Publication Data
A CIP record for this book is available from the British Library
ISSN 2051-2481 (Print)
ISSN 2051-249X (Online)
ISBN 978-1-84821-843-7

Physical Chemistry and Acid-Base Properties of Surfaces

Introduction

Capillarity is the study of interfaces between two immiscible liquids, between a liquid and air or between a solid and a liquid. These interfaces are able to change shape or even move in order to minimize the energy of the system.

This science started to be developed in the 19th Century by its founding fathers: Laplace and Young. More recently, different schools have developed the domain further. These include, among others, the Russian school with Derjagin, the Belgian school with Defay and Prigogine, the French school with Lippmann, Bouasse and de Gennes, and the American school with Fowkes, van Oss-Good and Israelachvili.

The last two decades have witnessed the significant development of studies of wettability, both experimentally and theoretically due to applications in different technological domains. This includes the areas of adhesive bonding in the production of metal/polymer interfaces, microelectronics with the development of molecular bonding, fuel cells with the need to manage water in a porous medium, the development of a knowledge-based approach to the cleanability of materials such as glass or stainless steel, and the value of electrowetting in the development of “Lab-on-a-chip” applications. The field now covered is considerable.

This book provides an overview of a Master’s level course developed by one of the authors over a 15-year period with engineering students and PhD students from the Phelma school of the *Institut Polytechnique* in Grenoble, France. The examples given are subjectively chosen by the authors, although they are guided by the importance and originality of the underlying applications.

Several domains are omitted such as those regarding, for instance, the spreading kinetics of a liquid or the elasticity of triple lines. Likewise experimental aspects linked to determining surface tensions are not presented in detail and refer to very thorough existing works which are indicated in the bibliography.

Following a reminder of the fundamental aspects of wettability regarding ideal and real surfaces, we focus on the study of various components of the interfacial tension. A review of the literature and its evolution, through the analysis of quantum mechanics, provides an understanding of Fowkes formulations on the one hand, and Van Oss and Good's on the other hand.

The use of this formalism from an experimental point of view is presented by conducting wettability experiments (one liquid and two liquid methods) and illustrated by examples.

Various experimental methods are then described in order to evaluate the acid-base properties of solid surfaces, on a macroscopic scale (mean overall measure) or on an atomic or molecular scale (identification of the acid or base nature of the various sites present on the surface).

Finally, the problem of charges at the solid-liquid interface, which is rarely addressed in the literature, is examined in detail using the concepts of the electrochemical double layer. This key issue is central to the concept of zero point of charge, i.e. the pH of the aqueous solution in contact which leads to an overall zero surface charge.

The situation of the zero point of charge is also characterized by a maximum in the solid-liquid interfacial tension.

Using these results, the wettability measurements taken as a function of the pH of the aqueous solution help to define the zero point of charge of different surfaces (usually oxides). Examples of model and industrial surfaces are given.

The same concepts also demonstrate how the injection of charges by a potential will lead to a reduction in the solid-liquid interfacial tension thus leading to a decrease in the contact angle at the origin of the electrowetting.

The latter effect is at the source of significant recent developments in the field of microfluidics. Generic configurations used are presented and illustrated by recent works taken from the literature.

Contents

Introduction	ix
Chapter 1. Wettability of an Ideal Surface: Overview	1
1.1. Wetting angle	1
1.2. Adhesion effect	4
1.3. Surface tension and free surface energy	5
Chapter 2. Real Surfaces	9
2.1. Wenzel's model – topological defects	9
2.2. Cassie–Baxter model: chemical defects.	11
2.3. Superhydrophilic surfaces	12
2.4. Superhydrophobic surfaces	16
2.5. Application	20
Chapter 3. Components of the Surface Energy	23
3.1. Overview	23
3.2. Molecular interactions and components of the energy.	26
3.3. The hydrogen bond	28
3.4. Lewis acid-base interactions	28
3.5. The effective components of the interaction energy	31
3.6. Application	32
Chapter 4. The Acid-Base Component in the Work of Adhesion	37
4.1. Overview	37
4.2. Use of the acid-base component.	38

4.3. The Owens–Wendt approximation	39
4.4. Van Oss–Good description	40
Chapter 5. Experimental Determination through Wettability Measurements	45
5.1. One liquid method	46
5.2. Two liquid method. Surfaces with high surface energy	48
5.3. Applications of the two liquid method	49
5.4. Comparison between Owens–Wendt and van Oss–Good methods	55
Chapter 6. Acid-Base Properties of Surfaces: Experimental Approaches	61
6.1. Overview	61
6.2. General methods	61
6.2.1. Wettability	61
6.2.2. Electrokinetic method	62
6.2.3. Scanning probe microscopies	68
6.2.4. Inverse gas chromatography at infinite dilution conditions	73
6.2.5. X-ray photoelectron spectroscopy (XPS)	78
6.2.6. Other methods	85
6.3. Local methods	86
6.3.1. Infrared spectroscopy	87
6.3.2. X-ray photoelectron spectroscopy (XPS)	91
6.3.3. Other methods	93
6.4. Application examples	94
6.4.1. Bonding ability of aluminum sheets	94
6.4.2. Mechanism of formation of the interphase in metal–polymer joints	96
6.4.3. Heterogeneous catalysis	98
Chapter 7. Oxide–Solution Interfaces: Surface Charges	99
7.1. Brønsted acidity and basicity	100
7.2. Point of zero charge (PZC)	101
7.3. The oxide–solution interface	103
7.4. Electrocapillarity in the oxide–solution interface	109
7.4.1. Evolution of the interfacial tension	110

Chapter 8. Electrocapillarity Applications	117
8.1. Study based on the pH of the oxide surfaces	117
8.2. Study of the stability of a liquid film on an oxide surface.	123
8.2.1. Case of a flat surface.	123
8.2.2. Case of a rough surface	125
8.3. Modification of the contact angle by an imposed potential (Electrowetting).	132
Conclusion	141
Bibliography	143
Index	153

Wettability of an Ideal Surface: Overview

1.1. Wetting angle

Young's relationship and definition of the work of adhesion.

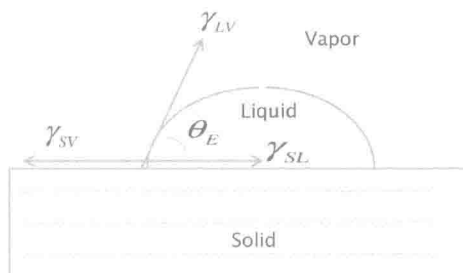


Figure 1.1. *Equilibrium of a liquid droplet on an ideal solid substrate*

When a liquid droplet is placed in a solid, it takes on a given configuration according to the interactions which take place between the solid and the liquid.

The system evolves toward a configuration of minimum free energy characterized by an angle of equilibrium θ_E .

If there is no chemical reaction at the solid–liquid interface, the geometry is simple, as shown in Figure 1.1.

Young's relationship [YOU 05] provides the equilibrium of forces at the triple line. Interfacial tensions are described as forces per unit of triple line length [DEF 66, DE 03]

$$\gamma_{SV} = \gamma_{SL} + \gamma_{LV} \cos \theta_E \quad [1.1]$$

where θ_E is the wetting angle and γ is the interfacial tension of solid–vapor, liquid–vapor and solid–liquid, respectively.

COMMENT 1.1.— γ_{SV} is the interfacial tension of the solid in equilibrium with the vapor phase. This value is generally different from the surface tension of the solid in equilibrium with vacuum or a neutral gas, denoted as γ_S . This difference is known as spreading pressure: π_e

$$\pi_e = \gamma_S - \gamma_{SV} \quad [1.2]$$

Young's equation can therefore be written as follows:

$$\gamma_S = \gamma_{SL} + \gamma_{LV} \cos \theta_E + \pi_e \quad [1.3]$$

The same result as Young's equation can be deduced from a virtual thermodynamic cycle (there are a number of different variations of this demonstration):

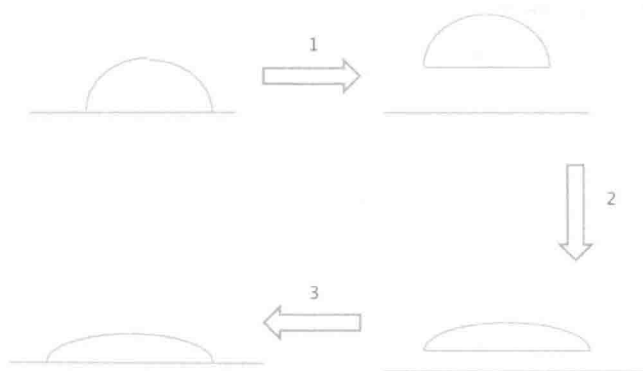


Figure 1.2. Virtual thermodynamic cycle for the equilibrium of a liquid droplet

Using a droplet with the interfacial area Ω placed on the solid, it can be assumed first that the droplet can be separated from the substrate without changing its shape.

$$\Delta G_1 = -\gamma_{SL}\Omega + \gamma_{SV}\Omega + \gamma_{LV}\Omega$$

Subsequently, the raised droplet undergoes a variation in contact area $d\Omega$ corresponding to the equilibrium situation. As a result, there is a variation in the area of the droplet cap: $d\Omega \cos\theta$ (Figure 1.3).

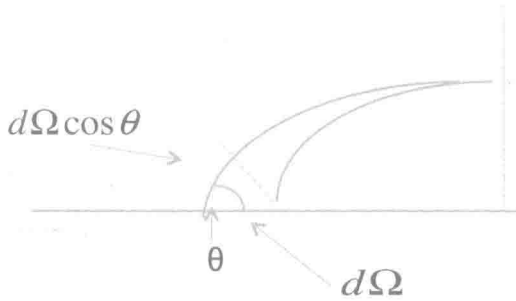


Figure 1.3. Area variation of the liquid droplet when it reaches the state of equilibrium

Hence: $\Delta G_2 = \gamma_{LV}d\Omega + \gamma_{LV}d\Omega \cos \theta.$

In the third stage, the droplet is placed back onto the solid:

$$\Delta G_3 = (\gamma_{SL} - \gamma_{SV} - \gamma_{SL})(\Omega + d\Omega)$$

The overall outcome is: $\Delta G = \Delta G_1 + \Delta G_2 + \Delta G_3.$

Hence: $\Delta G = (\gamma_{SL} - \gamma_{SV} + \gamma_{LV} \cos \theta_E) d\Omega.$

At equilibrium, this gives: $d\Delta G / d\Omega = 0.$

Hence: $\gamma_{SL} - \gamma_{SV} + \gamma_{LV} \cos \theta_E = 0.$

This does indeed bring us back to Young's equation.

1.2. Adhesion effect

Dupré definition, spreading coefficient.

The work of adhesion W_{SL} is the variation of free energy per unit area involved in the following transformation shown in the diagram in Figure 1.4.

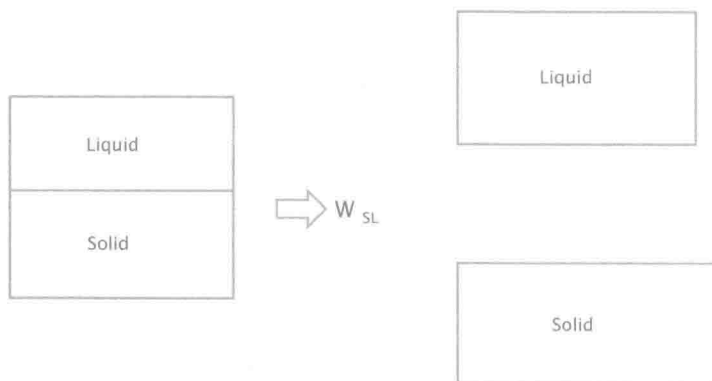


Figure 1.4. Definition of work of adhesion

The Dupré relationship is written as follows [DEF 66]:

$$W_{SL} = \gamma_S + \gamma_{LV} - \gamma_{SL} \quad [1.4]$$

In this definition, γ_S corresponds to a flat surface without vapor adsorption. The solid and liquid phases are very far away from each other.

The introduction of Young's relationship thus leads to the following expression:

$$W_{SL} = \gamma_{LV} (1 + \cos \theta_E) + \pi_e$$

This expression is too often reduced to the following one which ignores the spreading pressure without truly considering its relevance (see Chapter 3):

$$W_{SL} = \gamma_{LV} (1 + \cos \theta_E) \quad [1.5]$$

Indeed, the difference $\pi_e = \gamma_S - \gamma_{SV}$ can only be ignored in the case of a solid with low surface energy or if the vapor (water) adsorption only has a minor influence: polymers or oxides with a largely contaminated surface.

The ability of a solid for wetting by a liquid is shown by a strong adhesion effect and a low wetting angle.

Another parameter is also used to calculate wetting, which is the spreading coefficient S_e popularized by de Gennes [DE 03]:

$$S_e = \gamma_S - \gamma_{LV} - \gamma_{SL} \quad [1.6]$$

Using previous relationships, the spreading coefficient can be written as follows:

$$S_e = \pi_e - \gamma_{LV} (1 - \cos \theta_E) = W_{SL} - 2\gamma_{LV}$$

Extensive spreading of the liquid over the solid is obtained for positive spreading coefficients.

COMMENT 1.2.– Free energy of adhesion ΔF_a which is equal, apart from the sign, to the adhesion effect is a concept which is also widely used in the scientific literature.

1.3. Surface tension and free surface energy

Simplified analysis of surface tension and stresses for a solid or liquid surface. Relation with specific free surface energy.

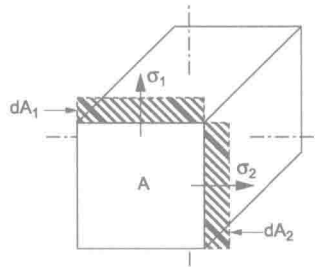


Figure 1.5. Reversible deformation of a face of a solid crystal

For the solid surface of a crystal, Figure 1.5 shows the reversible deformation at a constant temperature of the face of the crystal, slightly deformed by quantities dA_1 and dA_2 due to surface stresses σ_1 and σ_2 and in the absence of volume deformation:

$$\sigma_1 dA_1 + \sigma_2 dA_2 = d(AF_A)$$

where F_A is the specific free energy of the surface

with $F_A = U_A - TS_A$ (U_A : specific energy of the surface and S_A specific entropy of the surface).

For a symmetrical crystal or an isotropic solid, Shuttleworth shows that [SHU 50]:

$$\sigma_1 = \sigma_2 = \gamma_A$$

$$\gamma_A (dA_1 + dA_2) = \gamma_A dA = d(AF_A)$$

Hence:

$$\gamma_A = F_A + A \left(\frac{dF_A}{dA} \right) \quad [1.7]$$

For a liquid substrate which undergoes isothermal deformation at a constant volume, the second term of the previous equation is zero. Indeed, the atoms of the liquid are transferred to the surface and the number of atoms per unit area remains constant.

At low temperatures in the case of a solid, atoms are relatively immobile. After deformation, the number of atoms per unit area at a surface layer varies and dF_A/dA is not zero.

However, at high temperatures where diffusion is sufficient, it can be assumed that the number of atoms per unit area in the surface layer will remain relatively constant and therefore $dF_A/dA \approx 0$.

Hence:

$$\gamma_A \approx F_A \quad [1.8]$$

The complete thermodynamic analysis as proposed by Defay and Prigogine [DEF 66] helps to rigorously establish the useful relationships between the characteristic quantities of the surface.

We refer back to these simply by using their analogy with the thermodynamic relationships of the bulk phase, which are supposedly more familiar.

The definition of free enthalpy G is written as:

$$G = F + PV = \sum_i n_i \mu_i \text{ or by volume unit: } G_V = F_V + P = \sum_i c_i \mu_i$$

F_V represents the free energy per volume unit, c_i is the bulk concentration of the element i and μ_i its chemical potential.

This relation is written as: $-P = F_V - \sum_i c_i \mu_i$

By analogy, we obtain the following for the surface phase:

$$\gamma = F_A - \sum_i \Gamma_i \mu_i \quad [1.9]$$

Gibbs adsorptions are given by the expression $\Gamma_i = n_i^A / \Omega$ where n_i^A represents the excess in the number of moles of the constituent i on the uppermost surface compared to the bulk composition $n_i^A = n_i^s - n_i^b$ (rigorously for a division surface placed above the surface layer covering the homogeneous bulk phase) and Ω is the area of the surface.

The surface tension γ , similar, apart from the sign, to the bulk pressure, is expressed according to the specific free energy of the surface F_A , chemical potentials and Gibbs adsorptions Γ_i .

This relation shows that the surface tension γ is only reduced to the specific free energy of the surface F_A for a pure body or systems for which the adsorption Γ_i can be cancelled out by a suitable choice of the position of the division surface.

For multi-component systems where the temperature is such that diffusion can take place, there may be a segregation of one or more surfactant agents toward the surface or interface, causing an enrichment of the interface in surfactant elements and a reduction in the surface tension [DEF 66].

The variation in the free enthalpy G of a bulk phase can generally be written as follows:

$$dG = VdP - SdT + \sum_i \mu_i dn_i = d(\sum_i n_i \mu_i)$$

After simplification, this relation leads to the generalized Gibbs Duhem relationship, hence per volume unit:

$$dP_v = S_v dT + \sum_i c_i d\mu_i$$

By analogy, we can obtain the Gibbs adsorption equation:

$$d\gamma = -S_A dT - \sum_i \Gamma_i d\mu_i \quad [1.10]$$

This relationship will be used during the study of the solid–electrolyte interface in Chapter 7.

To conclude this short introduction, we predict that wettability studies will be important in various domains of application in material science.

At high temperatures, studies of this type will be necessary to address the issue of adhesion of different assemblies, such as, for example, ceramic–metal solder joints or the manufacturing of composite materials such as Al/SiC or Al/C.

At lower temperatures (close to ambient temperature), wettability studies help to establish the energy of solid surfaces, which can show structural defects and/or can be coated with a contamination layer (real case). It would therefore be possible to characterize the acid-base properties of the material studied, which is a quantity which guides in particular the adhesion of the now widely-used metal–polymer assemblies.