




Handbook of Nanocomposites

Rich Falcon

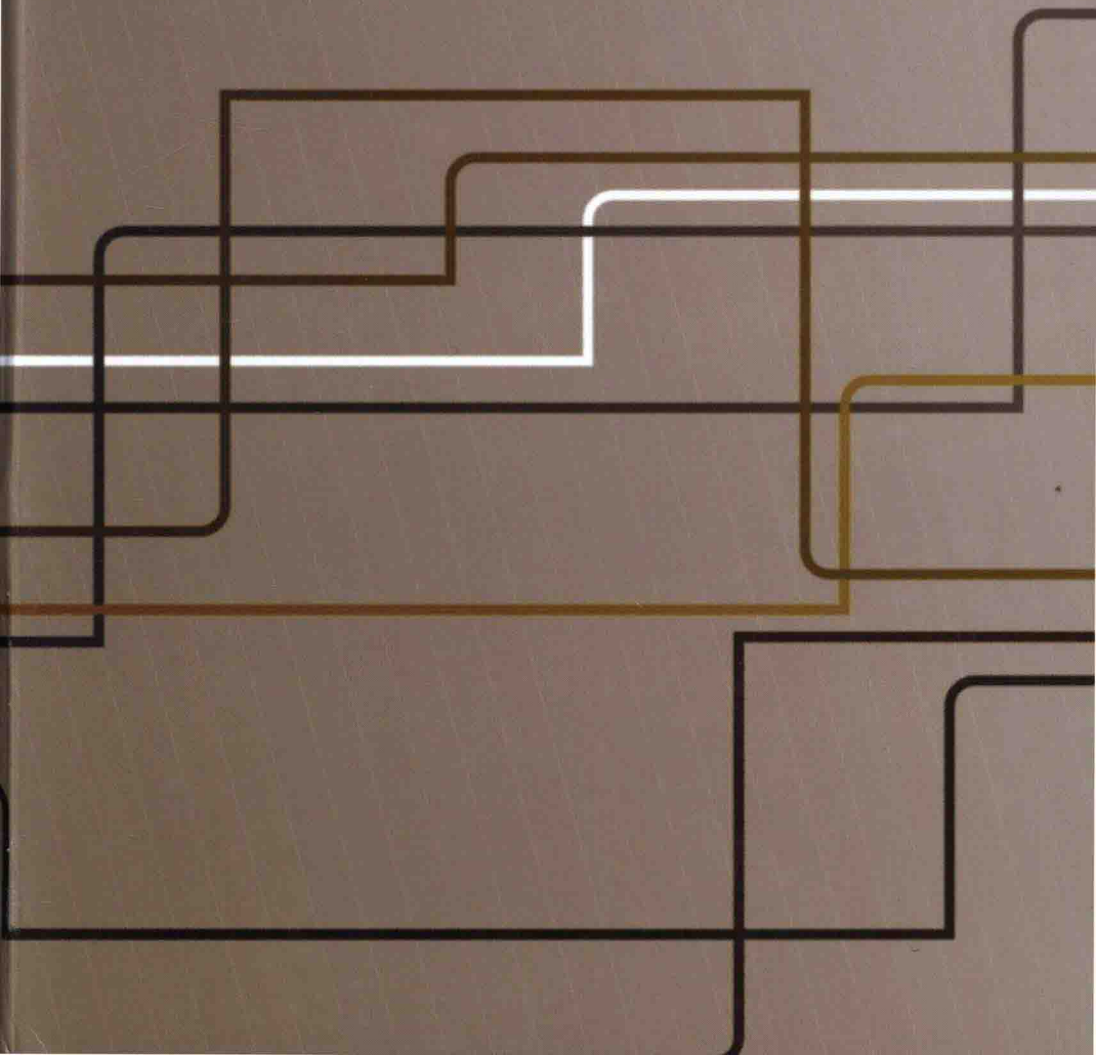

Handbook of Nanocomposites

Edited by **Rich Falcon**



NYRESEARCH
P R E S S

New York

Published by NY Research Press,
23 West, 55th Street, Suite 816,
New York, NY 10019, USA
www.nyresearchpress.com

Handbook of Nanocomposites
Edited by Rich Falcon

© 2015 NY Research Press

International Standard Book Number: 978-1-63238-257-3 (Hardback)

This book contains information obtained from authentic and highly regarded sources. Copyright for all individual chapters remain with the respective authors as indicated. A wide variety of references are listed. Permission and sources are indicated; for detailed attributions, please refer to the permissions page. Reasonable efforts have been made to publish reliable data and information, but the authors, editors and publisher cannot assume any responsibility for the validity of all materials or the consequences of their use.

The publisher's policy is to use permanent paper from mills that operate a sustainable forestry policy. Furthermore, the publisher ensures that the text paper and cover boards used have met acceptable environmental accreditation standards.

Trademark Notice: Registered trademark of products or corporate names are used only for explanation and identification without intent to infringe.

Printed in China.

Handbook of Nanocomposites

Preface

This book brings forth the experiences of experts from different scientific spheres across the world on their encounters with various aspects of nanocomposite science and its uses. The readers will be able to refer to research studies in the field of nanocomposites dealing with fundamental concepts and salient features of various nanocomposites like polymer/clay and polymer/carbon nanocomposites, composites of cellulose and metal nanoparticles and other kinds of nanocomposites. This handbook of nanocomposites will be a valuable reference for those interested in the field.

This book has been the outcome of endless efforts put in by authors and researchers on various issues and topics within the field. The book is a comprehensive collection of significant researches that are addressed in a variety of chapters. It will surely enhance the knowledge of the field among readers across the globe.

It is indeed an immense pleasure to thank our researchers and authors for their efforts to submit their piece of writing before the deadlines. Finally in the end, I would like to thank my family and colleagues who have been a great source of inspiration and support.

Editor

Contents

	Preface	VII
Chapter 1	Polymer/ Clay Nanocomposites: Concepts, Researches, Applications and Trends for The Future Priscila Anadão	1
Chapter 2	Polymer-Graphene Nanocomposites: Preparation, Characterization, Properties, and Applications Kuldeep Singh, Anil Ohlan and S.K. Dhawan	17
Chapter 3	Carbon Nanotube Embedded Multi-Functional Polymer Nanocomposites Jeong Hyun Yeum, Sung Min Park, Il Jun Kwon, Jong Won Kim, Young Hwa Kim, Mohammad Mahbub Rabbani, Jae Min Hyun, Ketack Kim and Weontae Oh	52
Chapter 4	Composites of Cellulose and Metal Nanoparticles Ricardo J. B. Pinto, Márcia C. Neves, Carlos Pascoal Neto and Tito Trindade	71
Chapter 5	High Performance PET/Carbon Nanotube Nanocomposites: Preparation, Characterization, Properties and Applications Jun Young Kim and Seong Hun Kim	95
Chapter 6	Polymer Nanocomposite Hydrogels for Water Purification Manja Kurecic and Majda Sfiligoj Smole	120
Chapter 7	Hard Nanocomposite Coatings, Their Structure and Properties A. D. Pogrebnjak and V. M. Beresnev	145

Chapter 8	Ecologically Friendly Polymer-Metal and Polymer-Metal Oxide Nanocomposites for Complex Water Treatment	183
	Amanda Alonso, Julio Bastos-Arrieta, Gemma.L. Davies, Yuri.K. Gun'ko, Núria Vigués, Xavier Muñoz-Berbel, Jorge Macanás, Jordi Mas, Maria Muñoz and Dmitri N. Muraviev	
Chapter 9	Impact Response of Nanofluid-Reinforced Antiballistic Kevlar Fabrics	210
	Roberto Pastore, Giorgio Giannini, Ramon Bueno Morles, Mario Marchetti and Davide Micheli	
Chapter 10	Graphene/Semiconductor Nanocomposites: Preparation and Application for Photocatalytic Hydrogen Evolution	234
	Xiaoyan Zhang and Xiaoli Cui	

Permissions

List of Contributors

Polymer/Clay Nanocomposites: Concepts, Researches, Applications and Trends for The Future

Priscila Anadão

Additional information is available at the end of the chapter

1. Introduction

On 29th December 1959, the physicist Richard Feynman delivered a lecture titled "There is plenty of room at the bottom" at the American Physical Society. Such a lecture is a landmark of nanotechnology, as Feynman proposed the use of nanotechnology to store information as well as a series of new techniques to support this technology [1]. From then on, the technological and scientific mastery of nanometric scale is becoming stronger due to the new research tools and theoretical and experimental developments. In this scenario, the worldwide nanotechnology market, in the next five years, is expected to be of the order of 1 trillion dollars [2].

Regarding polymer/clay nanocomposite technology, the first mention in the literature was in 1949 and is credited to Bower that carried out the DNA absorption by the montmorillonite clay [3]. Moreover, other studies performed in the 1960s demonstrated that clay surface could act as a polymerization initiator [4,5] as well as monomers could be intercalated between clay mineral platelets [6]. It is also important to mention that, in 1963, Greenland prepared polyvinylalcohol/montmorillonite nanocomposites in aqueous medium [7].

However, until the early 1970s, the minerals were only used in polymers as fillers commercially aiming to reduce costs, since these fillers are typically heavier and cheaper than the added polymers. During the 1970s, there was a vertiginous and successive increase in the petroleum price during and after the 1973 and 1979 crises [8]. These facts, coupled with polypropylene introduction in commercial scale, besides the development of compounds with mica, glass spheres and fibers, talc, calcium carbonate, led to an expansion of the ceramic raw materials as fillers and initiated the research as these fillers interacted with polymers.

Nevertheless, only in the late 1980s was the great landmark in the polymer clay nanocomposite published by Toyota regarding the preparation and characterization of polyamide 6/ organophilic clay nanocomposite to be used as timing belts in cars [9-11]. This new material, that only had 4.2 wt.%, had an increase of 40% in the rupture tension, 68% in the Young modulus and 126% in the flexural modulus as well as an increase in the heat distortion temperature from 65°C to 152°C in comparison with pure polymer [12]. From then on, several companies introduced thermoplastic nanocomposites, such as polyamide and polypropylene, in automotive applications [13]. Another highlighted application is as gas barrier, by using polyamides or polyesters [14].

2. Definitions

2.1. Polymer/ clay nanocomposites

Polymer/ clay nanocomposites are a new class of composites with polymer matrix in which the dispersed phase is the silicate constituted by particles that have at least one of its dimensions in the nanometer range (10^{-9} m).

2.2. Clays

The mineral particles most used in these nanocomposites are the smectitic clays, as, for example, montmorillonite, saponite and hectorite [15,16]. These clays belong to the phyllosilicate 2:1 family and they are formed by layers combined in a such a way that the octahedral layers that have aluminum are between two tetrahedral layers of silicon (Figure 1). The layers are continuous in the *a* and *b* directions and are stacked in the *c* direction.

The clay thickness is around 1 nm and the side dimensions can vary from 30 nm to various micrometers, depending on the clay. The layer stacking by Van der Waals and weak electrostatic forces originates the interlayer spaces or the galleries. In the layers, aluminum ions can be replaced by iron and magnesium ions, as well as magnesium ions can be replaced by lithium ions and the negative charge is neutralized by the alkaline and ferrous- alkaline cations that are between the clay layers. Moreover, between these layers, water molecules and polar molecules can enter this space causing an expansion in the *c* direction. This resulting surface charge is known as cation exchange capacity (CEC) and is expressed as mequiv/ 100g. It should be highlighted that this charge varies according to the layer and is considered an average value in the whole crystal [17-20].

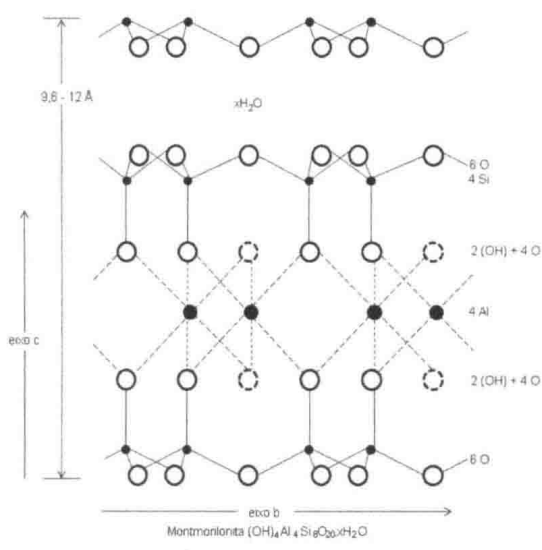


Figure 1. Schematic representation of montmorillonite.

2.3. Polymers

Polymers are constituted by largemolecules, called macromolecules, in which the atoms are linked between each other through covalent bonds. The great majority of the polymers are composed oflong and flexible chains whose rough sketch is generally made of carbon atoms (Figure 2). Such carbon atoms present two valence electrons notshared in the bonds between carbon atoms that can be part of the bonds between other atoms or radicals.

These chains are composed ofsmall repetitive units called *mero*. The origin of the word *meroderives* from the Greek word *meros*, which means part. Hence, one part is called by monomer and the word polymer means the presence of several *meros*.

When all the *meros* of the polymer are equal the polymer is a homopolymer. However, when the polymer is composed oftwo or more *meros*, the polymer is called copolymer.




Figure 2. Representation of an organic polymer chain.

Regarding the polymer molecular structure, polymers are linear when the *meros* are united in a single chain. The ramified polymers present lateral ramifications connected to the main chain. Polymers with crossed bonds have united linear chain by covalent bonds. Network

polymers have trifunctional *meros* that have three active covalent bonds, forming 3D networks (Figure 3)

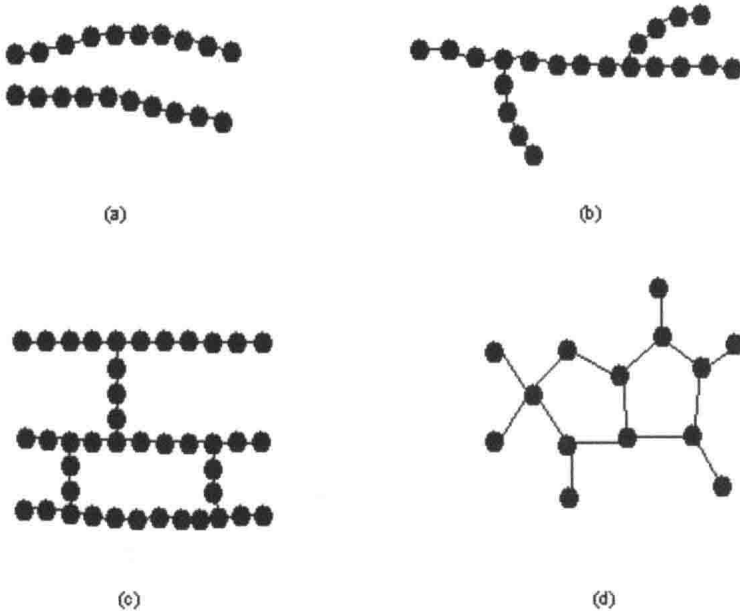


Figure 3. Schematic representation of: (a) linear, (b) ramified, (c) with crossed bonds and (d) network [21].

Polymers can be amorphous or semi-crystalline according to their structure. It is reasonable that the polymers that have a great number of radicals linked to the main chain are not able to have their molecules stacked as close as possible and, for this reason, the polymer chains are arranged in a disorganized manner, originating amorphous polymers. The polymers with linear chains and small groups are grouped in a more oriented form, forming crystals.

As a consequence of the polymer structure, there are two types of polymers: thermoplastic and thermofixes. Thermoplastic polymers can be conformed mechanically several times with reheating by the shear of the intermolecular bonds. Generally, linear and ramified polymers are thermoplastic and network polymers are thermofixes.

Thermofix polymers do not soften with temperature since there are crossed bonds in the 3D structure. Therefore, they cannot be recycled [21]

2.4. Polymer/ clay nanocomposite morphology

Depending on the interphase forces between polymer and clay, different morphologies are thermodynamically accepted (Figure4):

intercalated nanocomposite: the insertion of the polymer matrix in the silicate structure is crystallographically regular, alternating clay and polymer;

flocculated nanocomposites: it would be the same structure of the intercalated nanocomposite, except for the formation of floccus due to the interaction between the hydroxile groups of the silicate;

exfoliated nanocomposites: individual clay layers are randomly separated in a continuous polymer matrix at a distance that depends on the clay charge [22,23]

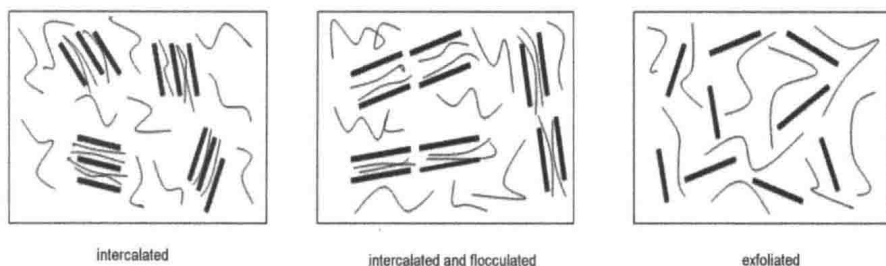


Figure 4. Polymer/ clay nanocomposites morphologies.

The formation and consequent morphology of the nanocomposites are related to entropic (ex.: molecular interactions) and enthalpic (changes in the configurations of the components) factors. Hence, efforts have been made to describe these systems. As an example, Vaia and Giannelis developed a model to predict the structure above according to the free energy variation of the polymer/ clay mixture in function of the clay layer separation.

The free energy variation, ΔH , associated to the clay layer separation and polymer incorporation is divided into two terms: the term related to the intern energy variation, ΔU , associated to the configuration changes of various components.

$$\Delta H = H(h) - H(h_0) = \Delta U - T\Delta S \quad (1)$$

Where h and h_0 are the initial and final separation of the clay layers. Then, when $\Delta H < 0$, the intercalation process is favorable.

Such model presents as a limitation the separation of the configuration term, the intermolecular interactions and the separation of the entropy terms of various components.

Other mathematical models were also developed for studies of simulation of the thermodynamics of the polymer/ clay nanocomposites. These models consider the nanocomposite thermodynamics and architecture, the interaction between clay and polymer to the free energy and the polymer and clay conformation.

Specifically for polyamide 6 and 66/ clay nanocomposites, the study of the molecular dynamics was employed, which uses the bond energy between the various components that composes the nanocomposite.

The kinetics of polymer/ clay nanocomposite formation is also a very important issue to predict the resulting nanocomposite. Studies of the molecular dynamics were also employed to understand the system kinetics. Other mathematical models were also used to describe the system kinetics, but kinetics is less understood than thermodynamics.

There is still the need of developing models that are explored in individual time and length scales, besides the integration of concepts that permeate from smaller to larger scales, that is, in the quantum, molecular, mesoscopic and macroscopic dominium [24].

2.5. Preparation methods of polymer/ clay nanocomposite

Three methods are widely used in the polymer/ clay nanocomposite preparation. The first one is the *in situ* polymerization in which a monomer is used as a medium to the clay dispersion and favorable conditions are imposed to carry out the polymerization between the clay layers. As clay has high surface energy, it performs attraction by the monomer units to the inside of the galleries until equilibrium is reached and the polymerization reactions occur between the layers with lower polarity, dislocating the equilibrium and then, aiming at the diffusion of new polar species between the layers.

The second method is solution dispersion. Silicate is exfoliated in single layers by using a solvent in which the polymer or pre-polymer is soluble. Such silicate layers can be easily dispersed in a solvent through the entropy increase due to the disorganization of the layers that exceed the organizational entropy of the lamellae. Polymer is then sorbed in the delaminated layers and when the solvent is evaporated, or the mixture is precipitated, layers are reunited, filled with the polymer.

Moreover, there is also the fusion intercalation, a method developed by Vaia et al. in 1993 [25]. In this method, silicate is mixed with a thermoplastic polymer matrix in its melted state. Under these conditions, the polymer is dragged to the interlamellae space, forming a nanocomposite. The driving force in this process is the enthalpic contribution of the interactions between polymer and clay.

Besides these three techniques, the use of supercritical carbon dioxide fluids and sol-gel technology can also be mentioned [26].

3. Polymer and clay modifications to nanocomposite formation

As explained before, the great majority of polymers are composed of a carbon chain and organic groups linked to it, thus presenting a hydrophobic character. On the other hand, clays are generally hydrophilic, making them, at a first view, not chemically compatible. Aiming to perform clay dispersion and polymer chains insertion, it is necessary to modify these materials.

There are two possibilities to form nanocomposites: clay organomodification that will decrease clay hydrophilicity and the use of a compatibilizing agent in the polymer structure, by grafting, to increase polarity. The concepts that govern each of these modifications will be explored in this chapter.

3.1. Clay organomodification

This method consists in the interlamellae and surface cation exchange (generally sodium and calcium ions) by organic molecules that hold positive chains and that will neutralize the negative charges from the silicate layers, aiming to introduce hydrophobicity and then, producing an organophilic clay. With this exchange, the clay basal space is increased and the compatibility between the hydrophilic clay and hydrophobic polymer. Therefore, the organic cations decrease surface energy and improve the wettability by the polymer matrix.

The organomodification, also called as organophilization, can be reached through ion exchange reactions. Clay is swelled with water by using alkali cations. As these cations are not structural, they can be easily exchanged by other atoms or charged molecules, which are called exchangeable cations.

The greater distance between the silicate galleries due to the size of the alkylammonium ions favor polymer and pre-polymer diffusion between the galleries. Moreover, the added cations can have functional groups in their structure that can react with the polymer or even begin the monomer polymerization. The longer the ion chain is and the higher the charge density is, the greater the clay layer separation will be [4,11].

3.2. Use of a compatibilizing agent

Generally, a compatibilizing agent can be a polymer which offers a chemically compatible nature with the polymer and the clay. By a treatment, such as the grafting of a chemical element that has reactive groups, or copolymerization with another polymer which also has reactive groups, compatibility between the materials will form the nanocomposite. Amounts of the modified polymer are mixed with the polymer without modification and the clay to prepare the nanocomposites.

Parameters such as molecular mass, type and content of functional groups, compatibilizing agent/ clay proportion, processing method, among others, should be considered to have compatibility between polymer and clay. Maleic anhydride is the organic substance most used to compatibilize polymer, especially with the polyethylene and polypropylene, since the polar character of maleic anhydride results in favorable interactions, creating a special affinity with the silicate surfaces [27,28].

4. The most important polymers employed in polymer/ clay nanocomposites

In this item, examples of studies about the most important polymers that are currently employed in the polymer/ clay nanocomposite preparation will be presented. For a better un-

derstanding, polymers are divided into general-purpose polymers, engineering plastics, conductive polymers and biodegradable polymers.

4.1. General-purpose polymers

General-purpose polymers, also called commodities, represent the majority of the total worldwide plastic production. These polymers are characterized by being used in low-cost applications due to their processing ease and low level of mechanical requirement. The formation of nanocomposites is a way to add value to these commodities.

4.1.1. Polyethylene (PE)

PE is one of the polymers that most present scientific papers related to nanocomposite formation. Maleic anhydride grafted PE/ Cloisite 20A nanocomposites were prepared by two techniques: fusion intercalation and solution dispersion. Only the nanocomposites produced by the first method produced exfoliated morphology. The LOI values, related to the material flammability, were lower in all composites and were highly reduced in the exfoliated nanocomposites due to the high clay dispersion [29].

Another work presented the choice of a catalyzer being supported on the clay layers that are able to promote *in situ* polymerization, besides exfoliation and good clay layer dispersion. The organophilic clays (Cloisite 20A, 20B, 30B and 93A) were used as a support to the Cp_2ZrCl_2 catalyzer. The higher polymerization rate was obtained with Cloisite 93A and the clay layers were dispersed and exfoliated in the PE matrix [30].

4.1.2. Polypropylene (PP)

Rosseau et al. prepared maleic anhydride grafted PP/ Cloisite 30B nanocomposites by water assisted extrusion and by simple extrusion. The use of water improved clay delamination dispersion and, consequently, the rheological, thermal and mechanical properties [29].

The use of carbon dioxide in the extrusion of PP/ Cloisite 20A nanocomposites enabled a higher separation between the clay layers. The use of clay at lower contents in the foam formation also suppressed the cell coalescence, demonstrating that the nanocomposite is also favorable to produce foams [31].

4.1.3. PVC

The use of different clays (calcium, sodium and organomodified montmorillonite, aluminum magnesium silicate clay and magnesium lithium silicate clay) was studied in the preparation of rigid foam PVC nanocomposites. Although the specific flexure modulus and the density have been improved by the nanocomposite formation, the tensile strength and modulus have their values decreased in comparison with pure PVC [32].